

Theory of Orbital Ordering, Fluctuation and Resonant X-ray Scattering in Manganites

Sumio Ishihara and Sadamichi Maekawa

Institute for Materials Research, Tohoku University, Sendai, 980-8577, Japan

(February 1, 2008)

A theory of resonant x-ray scattering in perovskite manganites is developed by applying the group theory to the correlation functions of the pseudospin operators for the orbital degree of freedom. It is shown that static and dynamical informations of the orbital state are directly obtained from the elastic, diffuse and inelastic scatterings due to the tensor character of the scattering factor. We propose that the interaction and its anisotropy between orbitals are directly identified by the intensity contour of the diffuse scattering in the momentum space.

PACS numbers: 75.30.Vn, 71.10.-w, 78.70.Ck

Since the discovery of colossal magnetoresistance, studies of perovskite manganites have been revived. One of the key factors to uncover the dramatic and fruitful phenomena in manganites is the orbital degree of freedom of manganese ions. The collective orbital ordered state as well as its fluctuation and excitation are investigated theoretically and experimentally. Recently, Murakami *et al.* have directly observed the orbital ordering (OO) by the resonant x-ray scattering (RXS) [1]. This technique reveals several characteristics of the degree of freedom through a variety of experiments, i.e. the polarization and temperature dependences of the scattering intensity and the diffuse scattering [2–6].

As compared with other scattering experiments, RXS is appropriate for observation of the orbital orderings and fluctuations. This is owing to the unique characters that (1) an anisotropy of the local electronic structure is detectable due to the tensor character of the scattering factor together with a short wave length of x-ray [7–9], and (2) this is a site selective technique by tuning an energy of the incident x-ray at the Mn *K*-edge. However, in spite of recent several theoretical approaches [9–12], a general theory of RXS by the orbital degree of freedom has not been presented.

In this letter, we develop a theory of RXS in manganites, for the first time, by applying the group theory to the correlation function of the pseudospin (PS) operators for the orbital degree of freedom. The obtained form of the cross section corresponds to those in the neutron scattering and in the conventional x-ray/electron scatterings as probes to detect spin and charge degrees of freedom, respectively. We show that static and dynamical informations of the orbital state are directly obtained by the elastic, diffuse and inelastic scatterings.

Let us formulate the scattering cross section in RXS. We consider the scattering of x-ray with momentum $\vec{k}_i$, energy ω_i and polarization λ_i to $\vec{k}_f$, ω_f and λ_f . The electronic state at the initial (final, intermediate) state in the scattering is described by $|i\rangle$ ($|f\rangle$, $|m\rangle$) with energy ε_i (ε_f , ε_m). The scattering cross section is given by [13,14]

$$\frac{d^2\sigma}{d\Omega d\omega_f} = A \frac{\omega_f}{\omega_i} \sum_{|f\rangle} |S|^2 \delta(\varepsilon_f + \omega_f - \varepsilon_i - \omega_i), \quad (1)$$

where

$$S = \sum_m \left\{ \frac{\langle f | \vec{j}_{-k_i} \cdot \vec{e}_{k_i \lambda_i} | m \rangle \langle m | \vec{j}_{k_f} \cdot \vec{e}_{k_f \lambda_f} | i \rangle}{\varepsilon_i - \varepsilon_m - \omega_f} + \frac{\langle f | \vec{j}_{k_f} \cdot \vec{e}_{k_f \lambda_f} | m \rangle \langle m | \vec{j}_{-k_i} \cdot \vec{e}_{k_i \lambda_i} | i \rangle}{\varepsilon_i - \varepsilon_m + \omega_i + i\Gamma} \right\}, \quad (2)$$

and $A = (e^2/mc^2)^2$. Γ indicates the damping of a core hole, $\vec{e}_{k\lambda}$ is the polarization vector of x-ray and $\vec{j}_k$ is the current operator divided by a factor $e/\sqrt{m}$. Eq. (1) together with Eq. (2) is rewritten by the correlation function of the electronic polarizability [14,15,8] as

$$\frac{d^2\sigma}{d\Omega d\omega_f} = A \frac{\omega_f}{\omega_i} \sum_{\alpha\beta\alpha'\beta'} P_{\beta'\alpha'} P_{\beta\alpha} \Pi_{\beta'\alpha'\beta\alpha}(\omega, \vec{K}), \quad (3)$$

where

$$\Pi_{\beta'\alpha'\beta\alpha}(\omega, \vec{K}) = \frac{1}{2\pi} \int dt e^{i\omega t} \sum_{ll'} e^{-i\vec{K} \cdot (\vec{r}_{l'} - \vec{r}_l)} \times \langle i | \alpha_{l'\beta'\alpha'}(t)^\dagger \alpha_{l\beta\alpha}(0) | i \rangle, \quad (4)$$

$\vec{K} = \vec{k}_i - \vec{k}_f$, $\omega = \omega_i - \omega_f$ and $P_{\beta\alpha} = (\vec{e}_{k_f \lambda_f})_\beta (\vec{e}_{k_i \lambda_i})_\alpha$. The polarizability operator at site l is defined by $\alpha_{l\beta\alpha}(t) = e^{iH_e t} \alpha_{l\beta\alpha}^{(\omega_i)} e^{-iH_e t}$ where H_e is the electronic part of the Hamiltonian and

$$\alpha_{l\beta\alpha}^{(\omega_i)} = i \int_{-\infty}^0 dt e^{-i\omega_i t} [j_{l\beta}(0), j_{l\alpha}(t)], \quad (5)$$

with $[\dots]$ being a commutator. Since RXS at the Mn *K*-edge is dominated by the electric dipole transition, $\vec{j}_k$ is given by the local current operator which is independent of $\vec{k}$ as $\vec{j}_k = \sum_l e^{-i\vec{k} \cdot \vec{r}_l} \vec{j}_l$.

The polarizability is expanded in terms of the PS operators for the orbital degree of freedom by utilizing the group theoretical analyses [16]. We consider the system where the point symmetry around a Mn ion is O_h and the doubly degenerate orbitals with the E_g symmetry

exist in each Mn^{3+} ion. The two bases in the E_g symmetry are denoted by e_{gu} and e_{gv} corresponding to the $3d_{3z^2-r^2}$ and $3d_{x^2-y^2}$ orbitals, respectively. The PS operators are defined as $T_{l\mu} = \frac{1}{2} \sum_{\gamma\gamma'\sigma} d_{l\gamma\sigma}^\dagger (\sigma_\mu)_{\gamma\gamma'} d_{l\gamma'\sigma}$ for $\mu = (0, x, y, z)$ where σ_0 is a unit matrix, σ_ν ($\nu = x, y, z$) are the Pauli matrix and $d_{l\gamma\sigma}$ is the annihilation operator of the e_g electron at site l with orbital γ and spin σ . These operators have the A_{1g} , E_{gv} , A_{2g} , and E_{gu} symmetries for $\mu = 0, x, y$ and z , respectively. The tensor part with respect to the polarization of x-ray has the $T_{1u} \times T_{1u}$ symmetry which is reduced to $A_{1g} + E_g + T_{1g} + T_{2g}$. Since the polarizability should have the A_{1g} symmetry, $\alpha_{l\beta\alpha}$ associated with a PS operator is represented as

$$\alpha_{l\beta\alpha} = \delta_{\alpha\beta} I_{A_{1g}} T_{l0} + \delta_{\alpha\beta} I_{E_g} \left(\cos \frac{2\pi n_\alpha}{3} T_{lz} - \sin \frac{2\pi n_\alpha}{3} T_{lx} \right), \quad (6)$$

where $(n_x, n_y, n_z) = (1, 2, 3)$ and $I_{A_{1g}(E_g)}$ is a coupling constant. We note the following characteristics in Eq. (6): (1) higher order terms with respect to $T_{l\mu}$ at the same site are reduced to this form by using the operator algebra, (2) T_{ly} does not appear, because the tensor part of $\alpha_{l\beta\alpha}$ does not include the A_{2g} symmetry, and (3) spin operators at a site are not included, because the spin-orbit coupling is quenched in a Mn ion. We neglect terms including $T_{m\neq l\mu}$ caused by the higher order processes of the electron hopping and the Coulomb interactions. By using Eq. (6), the cross section in Eq. (3) is expressed by the correlation function of the PS operators as

$$\Pi_{\beta'\alpha'\beta\alpha}(\omega, \vec{K}) = \delta_{\beta'\alpha'} \delta_{\beta\alpha} \frac{1}{2\pi} \int dt e^{i\omega t} \sum_{ll'} e^{-i\vec{K} \cdot (\vec{r}_{l'} - \vec{r}_l)} \times \sum_{\gamma, \gamma'=0,x,z} I_{\gamma'\alpha'} I_{\gamma\alpha} \langle T_{l'\gamma'}(t) T_{l\gamma}(0) \rangle, \quad (7)$$

with $I_{0\alpha} = I_{A_{1g}}$ and $I_{x(z)\alpha} = I_{E_g} \cos(-\sin) \frac{2\pi n_\alpha}{3}$. $\langle i | \dots | i \rangle$ is replaced by the thermal average $\langle \dots \rangle$. When the energy of the scattered x-ray is integrated out, the cross section is given by

$$\frac{d\sigma}{d\Omega} = A \sum_{\alpha\alpha'} P_{\alpha'\alpha'} P_{\alpha\alpha} \sum_{\gamma, \gamma'=0,x,z} I_{\gamma'\alpha'} I_{\gamma\alpha} S_{\gamma'\gamma}(\vec{K}), \quad (8)$$

with $S_{\gamma'\gamma}(\vec{K}) = \sum_{ll'} e^{-i\vec{K} \cdot (\vec{r}_{l'} - \vec{r}_l)} \langle T_{l'\gamma'} T_{l\gamma} \rangle$. The present results suggest that RXS directly observes the dynamical correlation function of the PS operators as a function of $\vec{K}$ and ω . This is highly in contrast to the Raman scattering which is limited to $\vec{K} = 0$.

The convincing candidate for the microscopic origin of the $T_{l\mu}$ dependent polarizability is the Coulomb interaction between Mn $4p$ and Mn $3d$ electrons $\langle \gamma_2 \alpha_2 | V | \gamma_1 \alpha_1 \rangle$ [9,10,17] where $\gamma_{1(2)}$ ($\alpha_{1(2)}$) indicates the orbital states of the Mn $3d$ ($4p$) electron, and V is the Coulomb interaction. The diagonal and off-diagonal components of the

interaction are expressed by the Slater integral $F_{0(2)}$ between the electrons as $\langle \gamma\alpha | V | \gamma\alpha \rangle = F_0 + \frac{4}{35} F_2 \cos(\theta_\gamma - \frac{2\pi m_\alpha}{3})$ and $\langle \bar{\gamma}\alpha | V | \gamma\alpha \rangle = \frac{4}{35} F_2 \sin(\theta_\gamma - \frac{2\pi m_\alpha}{3})$, respectively, where $(m_x, m_y, m_z) = (1, 2, 3)$, θ_γ is an angle describing the occupied orbital states as $|3d_\gamma\rangle = \cos(\frac{\theta}{2}) |d_{3z^2-r^2}\rangle - \sin(\frac{\theta}{2}) |d_{x^2-y^2}\rangle$, and γ ($\bar{\gamma}$) indicates the occupied (unoccupied) orbital. The first and second terms of $\langle \gamma\alpha | V | \gamma\alpha \rangle$ and $\langle \bar{\gamma}\alpha | V | \gamma\alpha \rangle$ give rise to the T_{l0} , T_{lz} and T_{lx} dependences of $\alpha_{l\beta\alpha}$, respectively.

We first apply the scattering cross section to the elastic scattering below the OO temperature T_{OO} . Let us consider the charge and orbital ordered states where both the reciprocal lattice vectors in the superlattices $\vec{G}_c$ and $\vec{G}_o$ are assumed to be parallel to the $\vec{a} + \vec{b}$ axis in the cubic coordinate. The orbital ordered state with two kinds of sublattices are denoted as (θ_A/θ_B) , and $\langle \tilde{T}_z \rangle = \frac{1}{2} \sum_{l=A,B} (\cos \theta_l \langle T_{lz} \rangle - \sin \theta_l \langle T_{lx} \rangle)$ is adopted as an order parameter. In the conventional experimental arrangement in RXS, the azimuthal angle ϕ is the rotating one of the sample with respect to the scattering vector, and the incident x-ray has a σ polarization [1,9]. From Eq. (8), the cross section is obtained as

$$\left. \frac{d\sigma}{d\Omega} \right|_{\sigma \rightarrow \lambda_f} = AN^2 \left| I_{\lambda_f}^c(\vec{K}) + I_{\lambda_f}^o(\vec{K}) \right|^2. \quad (9)$$

The charge components of the scattering amplitude are $I_\sigma^c(\vec{G}_o) = 2I_{A_{1g}} \langle T_0 \rangle$ and $I_\pi^c(\vec{G}_o) = I_{\sigma,\pi}^c(\vec{G}_c) = 0$, and the orbital ones are $I_{\lambda_f}^o(\vec{K}) = I_{E_g} \langle \tilde{T}_z \rangle \{ (\cos \theta_A \pm \cos \theta_B) P_{\lambda_f}^c + (\sin \theta_A \pm \sin \theta_B) P_{\lambda_f}^s \}$. Here, N indicates a number of Mn ions in the A sublattice, $\langle T_0 \rangle$ is the order parameter for charge, $+$ ($-$) is for $\vec{K} = \vec{G}_{c(o)}$ and $P_{\lambda_f}^{c(s)}$ is a function of the azimuthal and scattering angles [18]. In the following, we consider the cases of $\vec{K} = \vec{G}_o$ and $\vec{G}_c$, respectively. (1) $\vec{K} = \vec{G}_o$: Through the polarization measurements, we can judge whether the $(\theta_A / -\theta_A)$ -type of the orbital ordered state, such as the $(d_{3x^2-r^2}/d_{3y^2-r^2})$ - and $(d_{x^2-z^2}/d_{y^2-z^2})$ -types, is realized or not. By inserting the relation $\theta_B = -\theta_A$ into Eq. (9), we derive $d\sigma/d\Omega|_{\sigma \rightarrow \sigma} = 0$ and

$$\left. \frac{d\sigma}{d\Omega} \right|_{\sigma \rightarrow \pi} = AN^2 3I_{E_g}^2 \langle \tilde{T}_z \rangle^2 \sin^2 \theta_A \sin^2 \phi \cos^2 \theta_s, \quad (10)$$

which shows a two-fold symmetry for ϕ . These are clearly distinct from the results with the relation $\theta_B \neq -\theta_A$; $d\sigma/d\Omega|_{\sigma \rightarrow \sigma}$ is finite and $d\sigma/d\Omega|_{\sigma \rightarrow \pi}$ has a component of a four-fold symmetry for ϕ . It is experimentally observed that $d\sigma/d\Omega|_{\sigma \rightarrow \sigma} = 0$ and $d\sigma/d\Omega|_{\sigma \rightarrow \pi} \propto \sin^2 \phi$ [1–6]. Thus, we judge that the $(\theta_A / -\theta_A)$ -type of the orbital ordered state is realized in these compounds, although the value of θ_A is not determined by measurements at this reflection. (2) $\vec{K} = \vec{G}_c$: The $(\theta_A / -\theta_A)$ -type of the ordered state is assumed. At $\lambda_f = \sigma$, where the RXS experiments for the charge ordering are carried out [1,4–6], both I_σ^c and I_σ^o are finite. The latter

depends on ϕ and changes its sign with changing θ_A as $I_\sigma^o = I_{E_g} \langle \tilde{T}_z \rangle \frac{1}{2} \cos \theta_A (1 + 3 \cos 2\phi)$. Thus, the interference term of I_σ^o and I_σ^c is available to determine θ_A through measurements of the ϕ dependence of the cross section. On the other hand, at $\lambda_f = \pi$, the charge component is zero and the cross section is given by

$$\left. \frac{d\sigma}{d\Omega} \right|_{\sigma \rightarrow \pi} = AN^2 3I_{E_g}^2 \langle \tilde{T}_z \rangle^2 \cos^2 \theta_A \sin^2 2\phi \sin^2 \theta_s, \quad (11)$$

showing a four-fold symmetry for ϕ . By combining the measurements of $d\sigma/d\Omega|_{\sigma \rightarrow \pi}$ at $\vec{K} = \vec{G}_o$ (Eq. (10)) and at $\vec{K} = \vec{G}_c$ (Eq. (11)), a value of $|\tan \theta_A|$ can be obtained.

As shown in Eq. (10), $d\sigma/d\Omega|_{\sigma \rightarrow \pi}$ at $\vec{K} = \vec{G}_o$ is proportional to the factor $\sin^2 \theta_A$ as well as $\langle \tilde{T}_z \rangle^2$. It becomes maximum in the state of $\{\frac{1}{\sqrt{2}}(d_{3z^2-r^2} - d_{x^2-y^2})/\frac{1}{\sqrt{2}}(d_{3z^2-r^2} + d_{x^2-y^2})\}$ -type ($\theta_A = \pi/2$) rather than the $(d_{x^2-z^2}/d_{y^2-z^2})$ - ($\theta_A = \pi/3$) or $(d_{3x^2-r^2}/d_{3y^2-r^2})$ -types ($\theta_A = 2\pi/3$). It is experimentally reported that the cross section largely changes far below T_{OO} where $\langle \tilde{T}_z \rangle$ is expected to be saturated [1-3,5,6]. A dramatic increase in the cross section was observed especially in LaMnO₃ at low temperatures [2]. We propose that a possible mechanism of the anomalous temperature dependences is due to the change of the value of θ_A . In particular, the coupling between spin and orbital degrees of freedom can change θ_A near the magnetic transition temperature. In LaMnO₃, the increase in the factor $\sin^2 \theta_A$ with decrease in θ_A from $2\pi/3$ (the $(d_{3x^2-r^2}/d_{3y^2-r^2})$ -type) is supposed to be realized near the Néel temperature of the A-type antiferromagnetic state where the $(d_{x^2-z^2}/d_{y^2-z^2})$ -type ($\theta_A = \pi/3$) is stabilized [19,20].

We next apply the cross section in Eq. (8) to the diffuse scattering. Being based on the general model describing the interaction between PS operators $H = \frac{1}{2} \sum_{l,l',\gamma,\gamma'=x,z} T_{l'\gamma'} J_{\gamma'\gamma}(\vec{r}_{l'} - \vec{r}_l) T_{l\gamma}$ together with the random-phase approximation, the static correlation function $S_{\gamma'\gamma}(\vec{K})$ is obtained as

$$S_{\gamma'\gamma}(\vec{K}) = N\chi_0 T [1 + \chi_0 J(\vec{K})]_{\gamma'\gamma}^{-1}, \quad (12)$$

with $\chi_0 = 1/(4T)$. $S_{\gamma'\gamma}(\vec{K})$ around $\vec{K} = \vec{G}_o$ near T_{OO} contributes to the diffuse scattering in RXS. It is worth to note that, as shown in Eq. (8), an intensity contour of the diffuse scattering directly reflects the momentum dependence of $S_{\gamma'\gamma}(\vec{K})$ and each element of $S_{\gamma'\gamma}(\vec{K})$ with respect to γ and γ' is obtained by changing a polarization of x-ray. This is owing to the tensor character of the scattering factor and is highly in contrast to the conventional x-ray and neutron scatterings [21]; Unlike the present case, the intensity contour in those cases is not directly determined by $S_{\gamma'\gamma}(\vec{K})$ but the correlation function of charge, which connects with $S_{\gamma'\gamma}(\vec{K})$ through the momentum-dependent coupling constant between PS and lattice vibration, and the factor $\vec{K} \cdot \vec{e}_{jKs}$, where $\vec{e}_{jKs}$

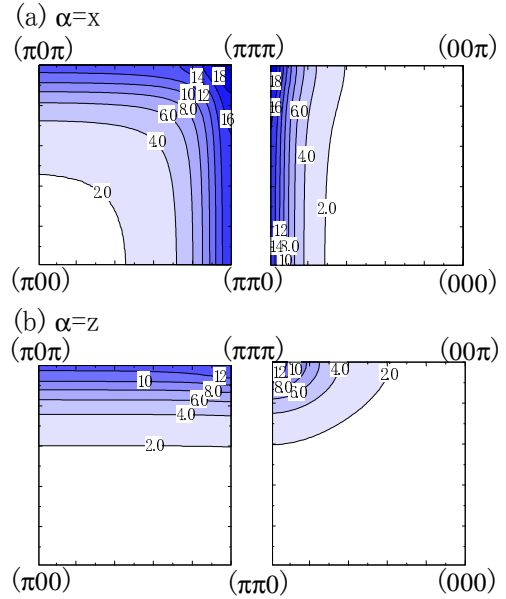


FIG. 1. The intensity contour of the diffuse scattering: $B_{\alpha\alpha}(\vec{K}) = (NT\chi_0 I_{E_g}^2)^{-1} \sum_{\gamma'\gamma} I_{\gamma'\alpha} I_{\gamma\alpha} S_{\gamma'\gamma}(\vec{K})$ at $T = 1.05T_{OO}$. (a) $\alpha = x$ and (b) $\alpha = z$ cases.

is the displacement vector of the j th ion for a normal coordinate with momentum $\vec{K}$ and mode s .

The above form of the diffuse scattering is applied to a case of OO in perovskite manganites where the interaction between orbitals is dominantly caused by the electronic process. The following Hamiltonian is adopted to calculate the intensity contour microscopically [22,23,3];

$$H = \sum_{\langle ij \rangle} \left(\frac{3}{2} J_1^l - \frac{1}{2} J_2^l \right) \tau_i^l \tau_j^l, \quad (13)$$

where $\tau_i^l = \cos(2\pi n_l/3)T_{iz} - \sin(2\pi n_l/3)T_{ix}$ with $(n_x, n_y, n_z) = (1, 2, 3)$, l indicates a direction of a bond between site i and its nearest neighboring j , and J_1^l and J_2^l are the superexchange-type interactions between PS's. This model is derived by the perturbational calculation of the electron hopping between Mn ions under the strong Coulomb interactions [22]. In Fig. 1, we present the calculated intensity contour of $B_{\alpha\alpha}(\vec{K}) = (NT\chi_0 I_{E_g}^2)^{-1} \sum_{\gamma'\gamma} I_{\gamma'\alpha} I_{\gamma\alpha} S_{\gamma'\gamma}(\vec{K})$ at $T = 1.05T_{OO}$ by which the cross section is represented as $d\sigma/d\Omega = A \sum_{\alpha'\alpha} P_{\alpha'\alpha} P_{\alpha\alpha} NT\chi_0 I_{E_g}^2 B_{\alpha'\alpha}(\vec{K})$. OO occurs at $\vec{G}_o = (\pi\pi\pi)$ below T_{OO} . Strong intensity appears along the $(\pi\pi\pi) - (\pi\pi 0)$ direction and other two equivalent ones. This feature is attributed to the unique character of the superexchange-type interaction between PS's that $J_{xx}(\vec{r}_l - \vec{r}_{l'} = a\hat{z}) = 0$, that is, the hopping integral between the $d_{x^2-y^2}$ and $d_{x^2-y^2}(3z^2-r^2)$ orbitals is zero in the z direction [24,25]. The diffuse scattering in RXS has been experimentally observed in Pr_{1-x}Ca_xMnO₃ [5], although the measurements were carried out along one direction in the Brillouin zone. In this technique, the

critical orbital fluctuation is directly observed around principal $\vec{G}_o$'s where the conventional x-ray scattering is forbidden in perovskite crystals. It is proposed that through observations of the characteristic features along the $(\pi\pi\pi) - (\pi\pi 0)$ and other equivalent directions with changing a polarization of x-ray, we can identify the superexchange-type interaction between orbitals.

The present form of the cross section is also appropriate for the study of the inelastic RXS due to the collective excitation in the orbital ordered state termed orbital wave (OW). The dispersion relations of OW have been examined in the Hamiltonian Eq. (13) with spin degree of freedom [17]. By applying the Holstein-Primakoff transformation to the PS operator in Eq. (7), the scattering cross section for OW is given by Eq. (3) with

$$\begin{aligned} \Pi_{\alpha'\alpha}(\omega, \vec{K}) = & \frac{N}{4} I_{E_g}^2 \sum_{\vec{q}\vec{G}} \sum_{\mu\mu'} e^{-i\vec{G}\cdot(\vec{r}_{\mu'} - \vec{r}_{\mu})} S_{\alpha'\mu'} S_{\alpha\mu} \\ & \times \sum_{\nu} \left\{ X_{\mu'\nu} X_{\mu\nu}^* (n_{\vec{q}}^{\nu} + 1) \delta(\omega - \omega_{\vec{q}}^{\nu}) \delta_{\vec{K} - \vec{q} + \vec{G}} \right. \\ & \left. + X_{\mu'\nu}^* X_{\mu\nu} n_{\vec{q}}^{\nu} \delta(\omega + \omega_{\vec{q}}^{\nu}) \delta_{\vec{K} + \vec{q} + \vec{G}} \right\}, \quad (14) \end{aligned}$$

where μ (ν) indicates the orbital sublattice (the mode of OW), $\omega_{\vec{q}}^{\nu}$ ($n_{\vec{q}}^{\nu}$) is the energy (number) of OW and $S_{\alpha\mu} = \sin(2\pi n_{\alpha}/3 - \theta_{\mu})$. $X_{\mu\nu} = V_{\mu\nu} + W_{\mu\nu}^*$ are the coefficients in the Bogoliubov transformation defined as $a_{\vec{q}}^{\mu} = \sum_{\nu} (V_{\mu\nu} \alpha_{\vec{q}}^{\nu} + W_{\mu\nu} \alpha_{-\vec{q}}^{\nu\dagger})$ where $a_{\vec{q}}^{\mu}$ ($\alpha_{\vec{q}}^{\nu}$) is the annihilation operator of the Holstein-Primakoff boson (the orbital wave). The above form of the cross section is analogous to that in the one-magnon neutron scattering unlike in the two-magnon Raman one, since one OW is possible to be excited in RXS. However, there is a clear distinction from the neutron scattering; the y component of the operator T_y is not included. This characteristic brings about the selection rule between $\vec{K}$ and the modes of OW wave as follows. We consider the orbital ordered state of the $(\theta_A/\theta_A + \pi)$ -type with $\vec{G}_o = (\pi\pi\pi)$ theoretically predicted in the ferromagnetic insulating state. It is shown from Eq. (14) that the acoustic (optical) mode of OW is separately measured at $h + k + l = \text{odd}$ (even). This is because T_{ly} does not appear in the cross section.

In summary, we develop a theory of RXS in perovskite manganites, for the first time, by applying the group theory to the correlation function of the PS operators. The tensor character of the scattering factor is essential in several kinds of scatterings due to the orbital degree of freedom. The present theory is applied easily to RXS in other compounds with the orbital degree of freedom.

The authors thank Y. Murakami, Y. Endoh, T. Arima, K. Hirota, M. Blume, D. Gibbs and J. P. Hill for their valuable discussions. The work was supported by Grant-in-Aid for Scientific Research Priority Area from the Ministry of Education, Science and Culture of Japan, CREST and NEDO. Part of the numerical calculation was per-

formed in the HITACS-3800/380 supercomputing facilities in IMR, Tohoku Univ.

-
- [1] Y. Murakami *et al.*, Phys. Rev. Lett. **80**, 1932 (1998).
 - [2] Y. Murakami *et al.*, Phys. Rev. Lett. **81**, 582 (1998).
 - [3] Y. Endoh *et al.*, Phys. Rev. Lett. **82**, 4328 (1999).
 - [4] K. Nakamura *et al.*, Phys. Rev. B **60**, 2425 (1999).
 - [5] M. v. Zimmermann *et al.*, Phys. Rev. Lett. **83**, 4872 (1999).
 - [6] Y. Wakabayashi *et al.*, (unpublished).
 - [7] D. H. Templeton and L. K. Templeton, Acta Cryst. A **38**, 62 (1982); A **39**, 29 (1983).
 - [8] V. E. Dmitrienko, Act. Cryst. A **40**, 89 (1984).
 - [9] S. Ishihara and S. Maekawa, Phys. Rev. Lett. **80**, 3799 (1998), and Phys. Rev. B **58**, 13449 (1998).
 - [10] S. Ishihara and S. Maekawa, cond-mat/9907255.
 - [11] I. S. Elfimov *et al.*, Phys. Rev. Lett. **82**, 4264 (1999), M. Benfatto *et al.*, Phys. Rev. Lett. **83**, 636 (1999), M. Takahashi *et al.*, J. Phys. Soc. Jpn. **68**, 2530 (1999).
 - [12] N. Ovchinnikova, and V. E. Dmitrienko, (unpublished).
 - [13] M. Blume, J. Appl. Phys. **57**, 3615 (1985).
 - [14] A. V. Kolpakov *et al.*, Sov. Phys. Usp. **21**, 959 (1978).
 - [15] T. Moriya, J. Phys. Soc. Jpn. **23**, 28 (1967), O. Sakai and M. Tachiki, J. Phys. Chem. Solids **39**, 269 (1978).
 - [16] The group theoretical analyses of the Raman scattering have been done for spin degree of freedom in Ref. [15] and B. S. Shastry and B. I. Shraiman, Phys. Rev. Lett. **65**, 1068 (1990).
 - [17] S. Ishihara and S. Maekawa, cond-mat/9812028.
 - [18] $P_{\sigma}^c = -\frac{1}{2} \sin^2 \phi + \cos^2 \phi$, $P_{\pi}^c = -\frac{3}{2} \sin \phi \cos \phi \sin \theta_s$, $P_{\sigma}^s = 0$ and $P_{\pi}^s = -\frac{\sqrt{3}}{2} \sin \phi \cos \theta_s$ where ϕ and θ_s are the azimuthal and scattering angles, respectively.
 - [19] K. I. Kugel and D. I. Khomskii, JETP Lett. **15**, 446 (1972).
 - [20] R. Maezono *et al.*, Phys. Rev. B **58**, 11583 (1998).
 - [21] M. Kataoka and Y. Endoh, J. Phys. Soc. Jpn. **48**, 912 (1980), H. Terauchi *et al.*, ibid. **32**, 1049 (1978).
 - [22] S. Ishihara *et al.*, Physica C **263**, 130 (1996), and Phys. Rev. B **55**, 8280 (1997).
 - [23] $J_1^l = t_{0l}^2/(U' - I)$ and $J_2^l = t_{0l}^2/U$ where t_{0l} is the hopping integral between the $3l^2 - r^2$ orbitals in direction l and U , U' and I are the intra-site Coulomb interactions in a Mn ion. The spin correlation in the Hamiltonian presented in Ref. [22] $\vec{S}_i \cdot \vec{S}_j$ is replaced by zero, since OO appears in the paramagnetic phase in several insulating manganites. A weak anisotropy in the exchange interactions is introduced by $J_1^{x(y)}/J_1^z = J_2^{x(y)}/J_2^z = \delta_{x(y)}$ to remove degeneracy of the orbital ordered state. These values are chosen to be $\delta_x = 1.05$ and $\delta_y = 1.025$ in Fig. 1.
 - [24] S. Ishihara *et al.*, Phys. Rev. B **56**, 686 (1997); see also L. F. Feiner *et al.*, Phys. Rev. Lett. **78**, 2799 (1997).
 - [25] In the actual compounds, the tilting of a MnO_6 octahedron may cause a small finite value of $J_{xx}(a\hat{z})$.